

Technical data sheet



Product: 3460

Manufacturer: 3M DEUTSCHLAND GMBH

Product group: KLEBSTOFF

Article group: DICHTMASSE

Download: 21.06.2024

3M™ SCOTCH-WELD™ EC-3460 HT FST

This data sheet was provided to you by Tewipack Uhl GmbH. The company tewipack Uhl GmbH assumes no responsibility for the topicality and the Accuracy of the information contained. The properties of the products can vary due to various influences such as composition and condition of the Substrate, impurities in or on the substrate, temperature and humidity at the Change storage and environmental conditions during use. Using this product in combination with other material, the customer is responsible for to check through our own tests whether the product is suitable for the planned combination and whether this combination delivers the expected results

Tewipack Uhl GmbH
Industriestraße 15
D-75382 Althengstett

Telephone:
+49(0)7051/9297-0
Fax:
+49(0)7051/9297-99

E-Mail:
info@tewipack.de
Website:
www.tewipack.de

Managing director:
Alexander Uhl,
Michael Uhl
HRB 330424
Amtsgericht
Stuttgart

Bank details:
Sparkasse
Sindelfingen
Pforzheim
Calw
BLZ 666 500
85
Konto 17 787

Commerzbank
Sindelfingen
BLZ 603 400 71
Konto 8 001 166

Vereinigte
Volksbank AG
Böblingen
BLZ 603 900 00
Konto 80 089
003

Postbank
Stuttgart
BLZ 600 100
70
Konto 146
294 708

3M™ Scotch-Weld™ EC-3460 HT FST


Structural Void Filling Compound

Product Description

3M™ Scotch-Weld™ 3460 HT FST (fire smoke toxicity) is a temperature resistant, one part structural void filling compound based on epoxy chemistry. It is designed for use on honeycomb sandwich structures as edge close-out, corner reinforcement, local reinforcement for mechanical fixation, or complex gap filling. The void filler is compatible with metal and non-metal constructions that are typically found in aircraft interiors. The cured material has excellent fire, smoke and toxicity properties, based on a halogen and antimony free FST System. It offers excellent chemical resistance and has good processing attributes due to its handling, extrusion, filling, grinding, and painting abilities.

Key Features

- Extrudable through both cartridge and dispensing systems
- High compressive strength from -55 °C to 175 °C
- Meets stand-alone FAR / JAR 25.853 and ABD 0031
- 100 % solids and free of shrinkage
- Cures to a rigid, solvent resistant material in one hour > 125 °C

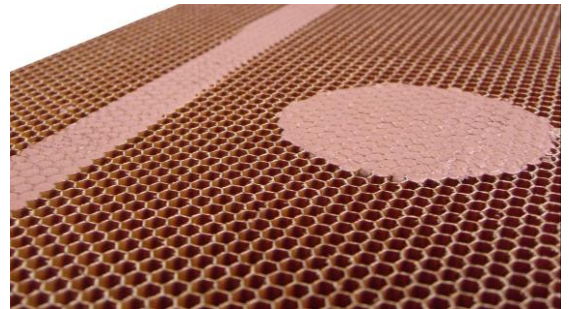

Product Characterization

The following technical information and data should be considered representative or typical only and should not be used for specification purposes.

General Properties	SW 3460 HT FST
Colour	Brown
Base	Modified epoxy
Work life ⁽¹⁾	> 3 days at 15 – 25 °C
Cured specific gravity	0.74 g/cm ³
Viscosity	Low flow, non-sag paste
Extrusion rate	> 100 g / minute
Volatiles loss on cure	Less than 1.5 %

¹ shop life is depending on application approach.

Product Performance

The following product performance data was obtained in the 3M Laboratory under the conditions specified. The following technical data should be considered as typical or representative only and should not be used for specification purpose. The values represent typical average product performance. The following cure cycles have been taken into account:

Cure Cycle 1: 60 minutes at 125°C in a heat press (heat rate 3 °C / minute)

Cure Cycle 2: 60 minutes at 175 °C in a heat press (heat rate 3 °C / minute)

Mechanical Properties	Temperature / Medium	Cure Cycle 1	Cure Cycle 2
Compressive strength ISO 604, specimen size 12.5 x 12.5 x 25 mm ³	-55 ± 2 °C	87 MPa	94 MPa
	23 ± 2 °C	68 MPa	71 MPa
	80 ± 2 °C	52 MPa	60 MPa
	120 ± 2 °C	29 MPa	45 MPa
	135 ± 2 °C	--	31 MPa
	150 ± 2 °C	--	18 MPa
	175 ± 2 °C	--	11 MPa
Compressive modulus ISO 604 (12.5 x 12.5 x 25 mm ³ specimens)	23 ± 2 °C	2.2 GPa	--
Resistance to fluids and fluid absorption ISO 604 Samples immersed in the environments for 1000 hours and tested at 23 ± 2 °C (absorption in wt.%)	Dry heat at 80 ± 2 °C	72 MPa	72 MPa
	Hot wet: 70 ± 2 °C, 85 % r. h.	62 MPa (0.33 %)	59 MPa (1.10 %)
	Demineralized water at 23 ± 2 °C	67 MPa (1.10 %)	61 MPa (1.02 %)
	Fuel JP4 at 23 ± 2 °C	68 MPa (0.40 %)	67 MPa (0.55 %)
	Skydrol 500B at 23 ± 2 °C	73 MPa (1.79 %)	67 MPa (2.19 %)

Flammability, Smoke Density and Toxic Gas Emission

All specimens for flammability, smoke density and toxic gas emission tests had a thickness of 4 mm.

Fire properties		Requirements	Cure Cycle 1	Cure cycle 2
Flammability 60 s vertical FAR/JAR/CS 25.853(a) App. F, part I(a)(1)(i)	Burn length	≤ 150 mm	--	1,3 mm
	After flame time	≤ 15 s	--	0 s
	Drips extinguishing time	≤ 3 s	--	0 s
Smoke density FAR/JAR/CS 25.853(d) App. F, part V(b)	DS _{max} ^(a) in 4 min	≤ 200	--	119
Toxic gas emission (flaming mode, stand-alone) Airbus ABD0031 Boeing D6-51377	HF	≤ 100 ppm	--	< 2 ppm
	HCl	≤ 150 ppm	--	2 ppm
	HCN	≤ 150 ppm	--	< 2 ppm
	SO ₂ + H ₂ S	≤ 100 ppm	--	< 20 ppm
	CO	≤ 1000 ppm	--	125 ppm
	NO + NO ₂	≤ 100 ppm	--	7 ppm

^(a) DS_{max}: maximum optical smoke density

Data are typical values and cannot be taken for specification purpose.

All Data were generated in stand alone test mode.

Handling, Application, Storage

Precautionary Information

Refer to product label and Material Safety Data Sheet (MSDS) for health and safety information before using this product. For MSDS visit our website www.3M.com/msds.

Instructions for use

Process step	Instruction
Surface preparation	A thoroughly cleaned, dry, grease-free surface is essential for maximum performance. For repeatable results the material and the substrates should be in the range of 20 - 25 °C object temperature.
Application	This product consists of one part. The material has to be unfrozen and conditioned to 20 – 25 °C before use. Note: The temperature has an influence on the product viscosity. Higher temperatures will generate lower viscosity. Product viscosity will increase on room temperature storage, which defines the shop life. Do not unfreeze more material than needed within shop life. For reproducible application results keep the product and substrate temperature in a constant range. Do not leave pails open if not used. Apply the product manually per spatula, or by semi- to full automation with an application device. Caution: Avoid excessive high application pressures. This may result in a density increase and change in performance.
Curing and processing	Cure the product at 125 °C or above (max. recommended curing temperature: 185 °C) in oven, heat press or autoclave. Keep heat rate in a range of 2 – 5 °C / minute. Higher temperatures generate faster curing times. The following times and temperatures will result in a full cure: <ul style="list-style-type: none">▪ 60 minutes at 125 ± 2 °C ; heat rate 2-5°C / minute▪ 50 minutes at 175 ± 2 °C; heat rate 2-5 °C / minute Finish the shape mechanically to desired shape after curing by using e.g. abrasive- or milling- processes. This product is paintable.
Cleaning	Excess uncured void filler can be cleaned with ketone type solvents. After cure, the adhesive can be removed mechanically. NOTE: When using solvents, extinguish all ignition sources, including pilot lights, and follow the manufacturer's precautions and directions for use.
Storage and handling	Store the product at -18 °C temperature or below. Shelf life at -18°C is minimum 3 months from date of shipment in the original unopened containers or cartridges. The specific expiry date is mentioned on the product label.

For additional information on this product contact your local 3M Aerospace Sales Representative or visit our homepage at www.3m.eu/aerospace.

Important notice: All statements, technical information and recommendations in this data sheet are based on tests 3M believes to be reliable, but the accuracy or completeness of those tests is not guaranteed. All technical data and information should be considered typical or representative only and should not be used for specification purposes. Given the variety of factors that affect the use and performance of a 3M product, some of which are uniquely within the user's knowledge and control, it is essential that the user evaluate the 3M product before use to determine the suitability of the 3M product for the intended use and method of application. All questions of liability relating to the 3M product are governed by the terms of the sale subject to, where applicable, the prevailing law.



Automotive and Aerospace Solutions Division
European Aerospace Laboratory

www.3m.eu/aerospace
Reference: 228

© 3M 2017. All rights reserved.