

# Technical data sheet



Product: 9

Manufacturer: 3M DEUTSCHLAND GMBH

Product group: ELEKTRO

Article group: VERGUSSMASSE

Download: 30.05.2026

## 3M™ SCOTCHCAST™ ELECTRICAL RESIN 9

This data sheet was provided to you by Tewipack Uhl GmbH. The company tewipack Uhl GmbH assumes no responsibility for the topicality and the Accuracy of the information contained. The properties of the products can vary due to various influences such as composition and condition of the Substrate, impurities in or on the substrate, temperature and humidity at the Change storage and environmental conditions during use. Using this product in combination with other material, the customer is responsible for to check through our own tests whether the product is suitable for the planned combination and whether this combination delivers the expected results

Tewipack Uhl GmbH  
Industriestraße 15  
D-75382 Althengstett

Telephone:  
+49(0)7051/9297-0  
Fax:  
+49(0)7051/9297-99

E-Mail:  
info@tewipack.de  
Website:  
www.tewipack.de

Managing director:  
Alexander Uhl,  
Michael Uhl  
HRB 330424  
Amtsgericht  
Stuttgart

Bank details:  
Sparkasse  
Sindelfingen  
Pforzheim  
Calw  
BLZ 666 500  
85  
Konto 17 787

Commerzbank  
Sindelfingen  
BLZ 603 400 71  
Konto 8 001 166

Vereinigte  
Volksbank AG  
Böblingen  
BLZ 603 900 00  
Konto 80 089  
003

Postbank  
Stuttgart  
BLZ 600 100  
70  
Konto 146  
294 708

# 3M™ Scotchcast™

## Electrical Resin 9

Two-Part, Room-Curing, Class B (130°C),  
Semi-flexible, Filled Epoxy Liquid Resin

Data Sheet

June 2016

### Description

3M™ Scotchcast™ Electrical Resin 9 is an easy-to-use resin system possessing medium viscosity and unique handling properties. It has a simple 1:1 mix ratio (by weight), and is frequently used in applications requiring excellent thermal shock and mechanical shock resistance. The resin's low exotherm and good pot life allow the user to mix substantial quantities at one time. High adhesion, low stress and low exotherm also reduce the effect of strain and temperature on sensitive components that have been coated with this resin.

- Good handling qualities
- Low exotherm
- Excellent thermal and mechanical shock resistance

<b>Handling Properties</b>	<b>Mix Ratio (A-B)</b>	Wt 1:1 Vol (%) 47:53
	<b>Viscosity @ 23°C (73°F)</b>	A = 90,000 cps B = 20,000 cps Mixed = 28,000 cps
	<b>Density</b>	A = 2.448 kg/l (12.08 lbs/gal) B = 1.280 kg/l (10.68 lbs/gal)
	<b>Flash Point</b>	A = 201°C (395°F) B = 180°C (356°F)
	<b>Gel Time</b>	28 min. @ 60°C (140°F)
	<b>Curing Guide</b>	23°C (73°F) 24-48 hrs 60°C (140°F) 2 hrs 95°C (203°F) 1 hr

# 3M™ Scotchcast™ Electrical Resin 9

## Typical Properties

Not for specifications. Values are typical, not to be considered minimum or maximum.  
Properties measured at room temperature 73°F (~23°C) unless otherwise stated.

Physical Property (*See Test Method Table)	Typical Value US units (metric)
<b>Color</b>	Brown
<b>Hardness (Shore D)</b>	70
<b>Specific Gravity (cured)</b>	1.42
<b>Compressive Strength*<sup>1</sup></b> 10% Compression	4400 psi (309 kg/cm <sup>2</sup> )
<b>Tensile Strength*<sup>2</sup></b> Ultimate	2200 psi (155 kg/cm <sup>2</sup> )
<b>Elongation (% at break)*<sup>2</sup></b>	19
<b>Flexural Strength*<sup>3</sup></b>	1100 psi (77 kb/cm <sup>2</sup> )
<b>Thermal Conductivity*<sup>4</sup></b> (Cal • cm/cm <sup>2</sup> • sec • °C)	7.4 x 10 <sup>-4</sup>
<b>Linear Thermal Expansion*<sup>4</sup></b> (23°C to 113°C) (length/unit length/°C)	13 x 10 <sup>-5</sup>
<b>Thermal Shock*<sup>4</sup></b>	Pass
<b>Thermal Shock*<sup>4</sup></b> 10 cycles – 55 to 130°C ¼" (6,35 mm) Olyphant Insert	Pass
<b>Electric Strength*<sup>5</sup></b> 1/8" (3,175 mm) sample	350 V/mil (13,8 kV/mm)
<b>Mechanical Shock*<sup>4</sup></b> Ball Drop (lbs)	7.75 (3,5 kg)
<b>Moisture Absorption*<sup>4</sup></b> % weight increase, 240 hrs. @ 96% R.H.	0.8
<b>Thermal Aging</b> % weight loss 1000 hrs. @ 130°C Hardness Change (Shore D)	2.5 +13
<b>Dielectric Constant*<sup>7</sup></b> 1000 Hz 23°C	4.6
<b>Dissipation Factor*<sup>7</sup></b> 1000 Hz 23°C	0.10
<b>Volume Resistivity*<sup>8</sup></b> 23°C (ohm-cm)	1 x 10 <sup>13</sup>
<b>Boiling Water Resistance</b> 7 Days - % weight gain - Hardness Change (Shore D)	2.5 -8
<b>Flammability*<sup>4</sup></b>	Self-extinguishing

### Test Methods

<sup>1</sup>Fed. Std. No. 406, Method 1021

<sup>2</sup>Fed. Std. No. 406, Method 1011

<sup>3</sup>Fed. Std. No. 406, Method 1031

<sup>4</sup>MIL-I-16923E

<sup>5</sup>Fed. Std. No. 406, Method 4031

<sup>6</sup>3M Test Method

<sup>7</sup>Fed. Std. No. 406, Method 4021

<sup>8</sup>Fed. Std. No. 406, Method 4041

# 3M™ Scotchcast™ Electrical Resin 9

## Usage Information

### Mixing

Mix the separate parts before removing them from their containers. They may be warmed to 60°C (140°F) to aid the mixing process. Thoroughly mix parts A and B in the correct proportions. Mix until the color is uniform or a homogeneous mixture is obtained.

### De-aerating

Air introduced during mixing can be removed by evacuating at 5 to 10 mm of mercury (Hg) absolute pressure. The 3M™ Scotchcast™ Electrical Resin can be warmed to aid air removal. The container sidewall should be four times the height of the liquid resin to contain the foaming that takes place under vacuum.

### Casting and Impregnating


Pour the warm resin into the preheated 100°C (212°F) mold. If no mold is used, dip the preheated part into the resin. Heating the part, resin and mold aids impregnation. Evacuate at 5 mm of mercury (Hg) absolute pressure, or pour under vacuum and hold for several minutes before releasing.

### Curing


Where minimum stress and maximum thermal shock resistance are required, the ambient temperature cure cycle is recommended. If an oven cure is used, time should be added to the cure cycle to allow the resin to reach the curing temperature. Cure using cycles shown under **Handling Properties**. Where higher temperatures are not objectionable and the size of the casting not excessive, the resin can be quick-cured in one hour at 95°C (203°F).

### Handling and Safety Precautions

Read all Health Hazard, Precautionary and First Aid statements found in the Material Safety Data Sheet (MSDS) and/or product label of chemicals prior to handling or use.

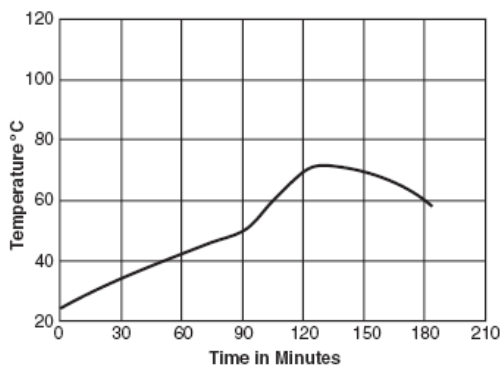

Exothermic Heat Rise for 1 lb. Sample

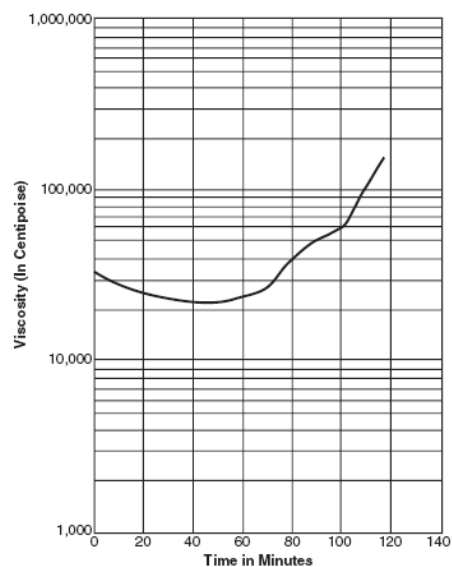


Brookfield Viscosity vs Time @ 73°F (23°C) 1 lb. sample

# 3M™ Scotchcast™ Electrical Resin 9

## Volume Resistivity (ohm-cm)


Fed. Std. No. 406, Method 4041

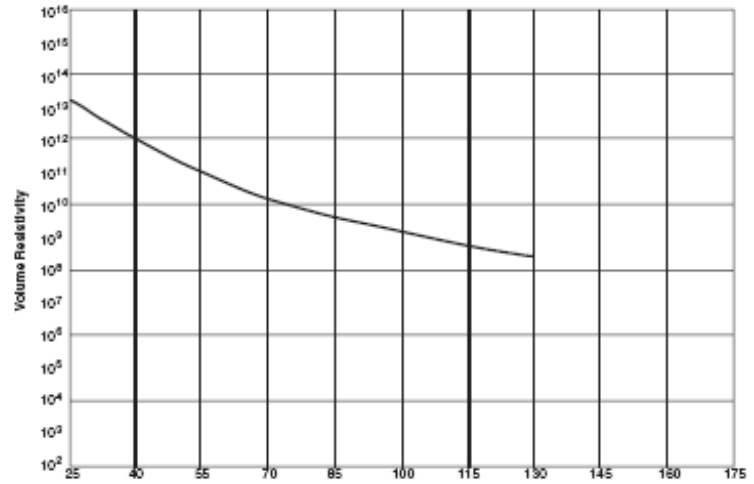

## Dissipation Factor %

Fed. Std. No. 406


(Test Frequencies in Hertz)

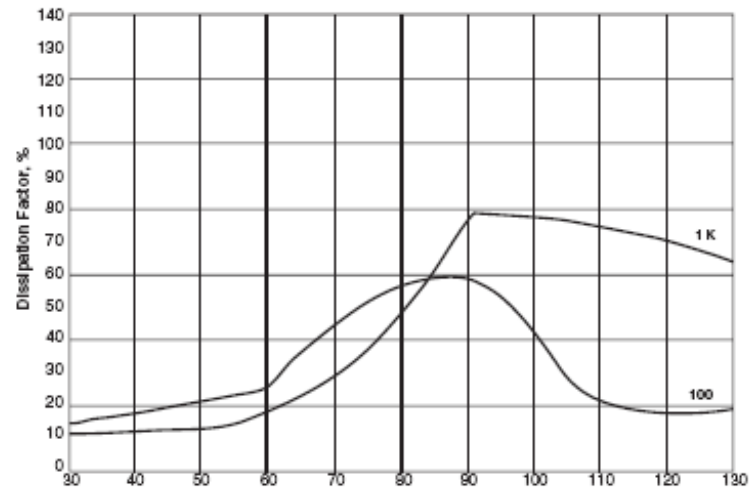

## Dielectric Constant

Fed. Std. No. 406, Method 4021

(Test Frequencies in Hertz)

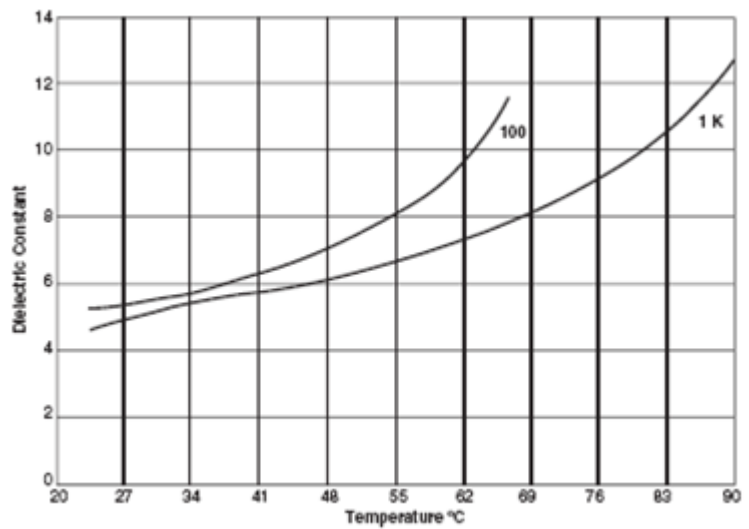

# 3M™ Scotchcast™ Electrical Resin 9

---

**Shelf Life & Storage** These resins have a 2 year shelf life following the date of manufacture when stored in a humidity controlled storage (10°C/50°F to 27°C/80°F and <75% relative humidity). It is 3M's standard procedure to ship any resin product with at least 50% of its shelf life remaining. Any special request for a specific shelf life requirement may require a larger than stated MOQ that justifies a non-scheduled product run. Contact your 3M sale representative or Customer Service for specific shelf life MOQ requirements. No product returns will be accepted on special shelf life request orders.

---

**Availability** Please contact your local distributor; available from [3M.com/electrical](http://3M.com/electrical) [Where to Buy] or call 1-800-676-8381.

---

---

**Important Notice** All statements, technical information, and recommendations related to 3M's products are based on information believed to be reliable, but the accuracy or completeness is not guaranteed. Before using this product, you must evaluate it and determine if it is suitable for your intended application. You assume all risks and liability associated with such use. Any statements related to the product, which are not contained in 3M's current publications, or any contrary statements contained on your purchase order, shall have no force or effect unless expressly agreed upon, in writing, by an authorized officer of 3M.

---

**Warranty; Limited Remedy; Limited Liability** This product will be free from defects in material and manufacture at the time of purchase. **3M MAKES NO OTHER WARRANTIES INCLUDING, BUT NOT LIMITED TO, ANY IMPLIED WARRANTY OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE.** If this product is defective within the warranty period stated above, your exclusive remedy shall be, at 3M's option, to replace or repair the 3M product or refund the purchase price of the 3M product. **Except where prohibited by law, 3M will not be liable for any direct, indirect, special, incidental or consequential loss or damage arising from this 3M product, regardless of the legal theory asserted.**

---

3M and Scotchcast are trademarks of 3M Company.



## Electrical Markets Division

6801 River Place Blvd.  
Austin, TX 78726-9000  
800.676.8381  
FAX: 800.828.9329  
[www.3M.com/oem](http://www.3M.com/oem)

Please recycle  
© 3M 2016 All rights reserved  
78-8124-5590-1 Rev E